

# MACRO DEFECT FREE CEMENTS: A REVIEW

OZGUR EKINCIOGLU<sup>1</sup>, M. HULUSI OZKUL<sup>1</sup>, and SILVIA PATACHIA<sup>2</sup>

<sup>1</sup>*Dept of Civil Engineering, Istanbul Technical University, Istanbul, Turkey*

<sup>2</sup>*Dept of Product Design, Mechatronics and Environment, Transilvania University of Brasov, Brasov, Romania*

The usage of polymers in different sectors has been increasing in recent decades, and even our current age may have been defined as polymer age. When concrete is considered polymers are also widely used to modify the properties of both mortar and concrete and the usage of polymers in concrete dates back to 1920's. On the other hand, Macro-defect free (MDF) cements are one particular type of cement-polymer composites and developed and patented by scientists at Imperial College at the beginnings of 1980's. MDF cements are produced by mixing cement (commonly calcium aluminate cement) with small amounts of polymer (usually polyvinyl alcohol acetate) and water. High shear, relatively low pressure (about 5 MPa) and moderate temperature (about 80-100 °C) are applied during the production of this material. MDF cements, although consist of more than 80% by weight of cement, show 20-30 times higher flexural strength comparing to ordinary Portland cements. However, MDF cements show a considerable reduction in strength when they are exposed to water even for a short time. Many studies have been conducted to solve the water sensitivity of MDF cements for over 30 years. In this study, production, basic properties and the current state of the art of MDF cements are explained, and the future research works are suggested.

*Keywords:* MDF composites, cement, polymer, calcium aluminate cement, PVA, water sensitivity.

## 1 INTRODUCTION

Concrete, mainly made with aggregates, cement and water, is the most consumed man-made material in the world. In addition to main ingredients, many additives are used in the production of concrete for different purposes. Notably, various types of polymers are used in concrete and mortar production to enhance the fresh and hardened state properties. The first usage of polymers in concrete dates back to 1924 (Ohama 1995). Polymer modification of cementitious materials has been witnessed to the innovation of polymer-modified materials with the improvement in polymer technology, and many different cement-polymer composites were produced since then.

Macro-Defect Free (MDF) cements are one example of a very broad field of cement-polymer composites, and had been developed and patented by Birchall *et al.* (1981, 1983) at Imperial College. The MDF cement can be prepared by using cement, polymer and water. 80-90% of this composite consists of cement by weight, while 10-15% is water and 1-7% is polymer (Ekincioglu 2009). Many researches had been conducted about MDF cements in last 30 years. In this study, a brief review of MDF

cements is given. The main materials used, production processes, properties and limitations are summarized in detail. Also, some promising attempts to improve the durability properties are mentioned.

## 2 MDF CEMENT PRODUCTION PROCESSES

### 2.1 Materials

Different cement and polymer combinations have been used for the production of MDF cements. Calcium aluminate cement (CAC) (Russell 1991, Ekincioglu 2009) and poly(vinyl alcohol) (PVA) (Birchall 1983, Santos 1999, Ekincioglu *et al.* 2012a) are the most widely utilized materials for the production of MDF cements. Besides CAC, Portland cements and slag cements were also used (Sinclair and Groves 1984, Poon and Groves 1988, Titchell 1991, Poon *et al.* 1998, Santos *et al.* 1999) in productions. Polyacrylamide (Sinclair and Groves 1985, Poon and Groves 1988, Ohama 1993, Poon 1998), cellulosic products (Eden and Bailey 1984, Drabik *et al.* 1994, Drabik *et al.* 1999, Drabik *et al.* 2001, Mojumdar 2001) and alcohol soluble polymers such as phenol resin precursors (Hasegawa *et al.* 1995, Pushpalal *et al.* 1997, Walberer and McHugh 1998, Pushpalal *et al.* 1999) were proposed as polymers for the productions of MDF cement. The approximate flexural strength of most typical MDF cement combinations can be seen in Figure 1.

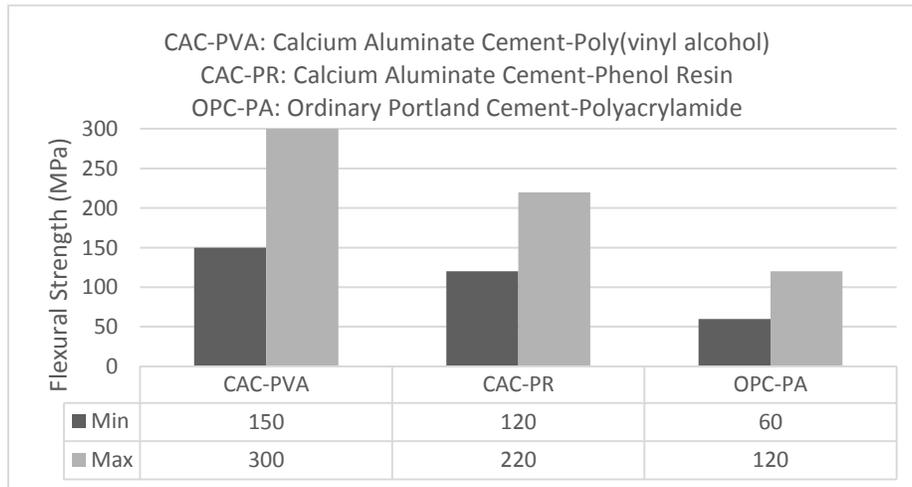


Figure 1. Approximate flexural strength of different MDF cement combinations.

### 2.2 Production Methods

Birchall *et al.*'s (1981, 1983) production method by applying high shear was generally accepted for as the standard MDF cement production procedure. This process was optimized by Russell (1991) and later Ekincioglu (2009). Another production method, Banbury type mixer for high shearing, was introduced by Tan (1992). Basic steps followed in the production and testing of MDF cements by Ekincioglu (2009) can be seen in Figure 2.

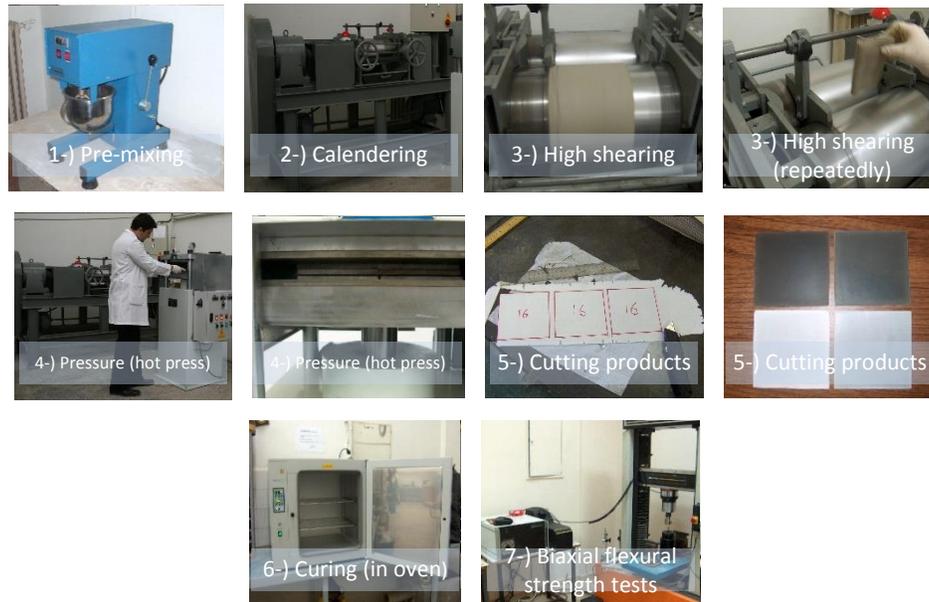


Figure 2. Basic steps to produce and test MDF cements (Ekincioglu 2009).

### 3 PROPERTIES OF MDF CEMENTS

#### 3.1 Mechanical Properties

Cement-based materials are known with their high compressive strength, but low tensile strength. On the other hand, MDF cements have superior mechanical properties both in compression and tension. However, they can be produced with various cement and polymer types, and their properties largely depend on the used materials. Comparison of some general properties of OPC, CAC-PVA and CAPR MDFs are shown in Table 1. As can be seen in Table 1, flexural strengths of MDF cements are 20-30 times higher than those of conventional (plain) cement pastes and nearly equal to that of an ordinary steel.

Table 1. Typical properties of OPC and MDF cement composites (Ekincioglu 2009).

Property	OPC	CAC-PVA MDF*	CAPR MDF**
Flexural Strength, MPa	5-10	150-300	120-200
Compressive Strength, MPa	40-60	380	300
Young's Modulus, GPa	20-30	40-50	32-45
Density, g/cm <sup>3</sup>	2,3	2,5	2.2-2.3

\*Polymer was PVA and the cement was alumina cement (Russell 1991).

\*\*Polymer was phenol resin and the cement was alumina cement (Pushpalal *et al.* 1999).

The high strengths of MDF composites are obtained by both the eliminating of macropores in the composite during processing and also the crosslinking formed between cement and polymer. Studies (Rodger *et al.* 1984, 1985, Popoola *et al.* 1991) showed that crosslinking reactions between polymer chains and metal ions generated

during the hydration reaction of cement are responsible for achieving such high strengths. On the other hand, MDF cements have serious durability problems. High strength losses are observed when they are exposed to water.

### 3.2 Durability Properties

The water sensitivity of MDF cements limits the usage of them in commercial applications. Therefore, many researchers have focused on this issue. Several different additives are used in MDF cement productions to prevent this problem. Some of the used additives are; alkali metal silicates (Lynn and Durey 1992), cross-linking chemicals (Desai 1992, Liutkus and Kovac 1988, Lewis and Boyer 1995), gypsum (Brown 1996),  $\text{CaCl}_2$  and  $\text{ZnCl}_2$  (Poon 1998), silica fume (Santos *et al.* 1999), activated carbon (Chowdhury 2004a, Chowdhury 2004b), epoxy resin (Ekincioglu *et al.* 2011) and  $\text{TiO}_2$  (Ekincioglu *et al.* 2012b). All these studies provided a better understanding of MDF cements, although none of them ultimately reduced the moisture sensitivity.

MDF cements are mostly produced with alumina cements and poly(vinyl alcohols), and the effects of the type of these most common ingredients were also investigated recently by Ekincioglu (2009). In a first study, MDF cements were produced with seven different types of poly(vinyl alcohol-co-vinyl acetate) (PVA) copolymers with various hydrolysis degrees (between 79.6% and 99.1%) and their effects on the mechanical properties were investigated. All specimens prepared were adversely affected by moisture. However, the lowest strength losses were obtained with the least hydrolysis degree PVA (79,6 mole%). Increasing the degree of hydrolysis of PVAs increased the strength loss of MDF specimens which were stored in water. MDF cements could not be produced with fully hydrolyzed PVA or carboxylated PVA. In the second part of the study, the effect of  $\text{Al}_2\text{O}_3$  content of alumina cements on the moisture sensitivity was investigated. Decreases in strength after 28 days water storage for w/c ratios between 0.09 and 0.19 shown in Figure 3. It seems that there is a minimum strength loss between 49% and 70% alumina contents of cement. Optimum  $\text{Al}_2\text{O}_3$  content for the lowest strength loss was found approximately 58%.

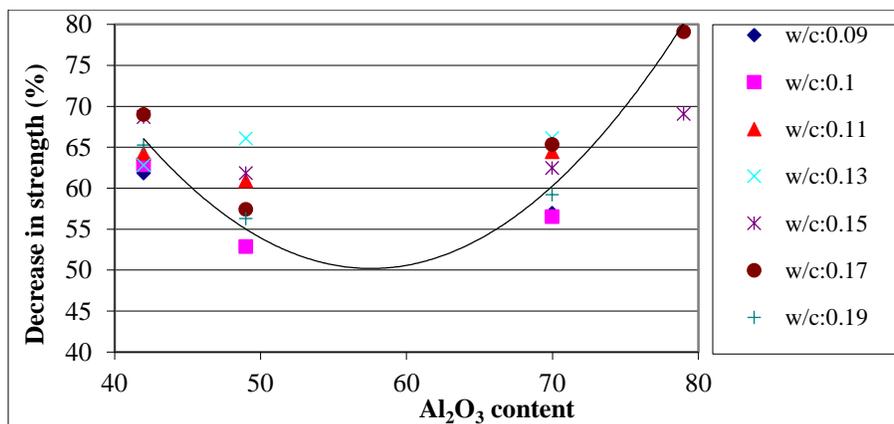


Figure 3. Strength loss versus  $\text{Al}_2\text{O}_3$  content in cement for 28 days water storage.

## 4 CONCLUSIONS

MDF cements are cement-polymer composites and show superior mechanical properties. Special production techniques by using calendaring are necessary to obtain high mechanical strengths. However, it is a brittle material, and especially the durability problems in water have limited its usage in any commercial application. Research activities about MDF cements have also declined in recent years due to durability problems. Many different additives, such as the addition of epoxy resin or  $\text{TiO}_2$ , were proposed to overcome the water sensitivity of MDF cements. Although some of them are promising, none of the proposed solutions completely solved this problem. A better understanding of crosslinking between the polymer and cement may allow us to produce water-resistant MDF cements. One area, which has not been sufficiently researched, is that coating MDF cements with a protective layer. MDF cements have superior properties and deserve further studies.

## References

- Birchall, J. D., Howard, A. J., and Kendall, K., Flexural strength and porosity of cements, *Nature*, 289(29), 388-390, 1981.
- Birchall, J. D., Howard, A. J., Kendall, K., and Raistrick, J. H., Cement composition and product, *United States Patent*, No: 4410366, 1983.
- Brown, J. L., Cement products and a method of manufacture thereof, *United States Patent*, No: 5514744, 1996.
- Chowdhury, B., Investigations into the role of activated carbon in a moisture-blocking cement formulation, *Journal of Thermal Analysis and Calorimetry*, 78(1), 215–226, Oct, 2004a.
- Chowdhury, B., Method for using activated carbon for producing moisture-blocking durable cement, composition for the same and method of characterizing the same, *United States Patent*, No: 6797052, 2004b.
- Desai, P. G., *Cement Polymer Interactions in Macro-Defect-Free Composites*, M.S. Thesis, University of Illinois at Urbana-Champaign, IL, USA, 1992.
- Drabik, M., Galikova, L., Kubranova, M., and Slade, R. C. T., Studies of Model Macroscopic-Defect-Free Materials Part 1- Investigations of the System  $4\text{CaO}\cdot\text{Al}_2\text{O}_3\cdot\text{Fe}_2\text{O}_3\cdot 4\text{CaO}\cdot 3\text{Al}_2\text{O}_3\cdot\text{SO}_3\text{-Hpmc-H}_2\text{O}$  by X-Ray, Thermoanalytical and NMR Techniques, *Journal of Materials Chemistry*, 4(2), 265-269, Feb, 1994.
- Drabik, M., Galikova, L., and Zimmermann, P., Attack by Moisture on Advanced Cement-Based Macroscopic Defect-Free Materials: A Thermoanalytical Study, *Journal of Thermal Analysis and Calorimetry*, 56(1), 117-124, Jul, 1999.
- Drabik, M., Mojumdar, S. C., and Galikova, L., Changes of Thermal Events of Macro Defect Free (MDF) Cements Due to the Deterioration in the Moist Atmosphere, *Cement and Concrete Research*, 31(5), 743-747, May, 2001.
- Eden, N. B., and Bailey, J. E., The mechanical properties and tensile failure mechanism of a high strength polymer modified Portland cement, *J Mater Sci*, 19(8), 2677–90, Aug, 1984.
- Ekincioglu, O., *Investigations of Moisture Sensitivity in Macro Defect Free Cements*, PhD Thesis, Istanbul Technical University, Istanbul, Turkey, 2009.
- Ekincioglu, O., Ozkul, M. H., Ohama, Y., Patachia, S., and Moise, G., Effect of Epoxy Resin Addition on the Moisture Sensitivity of Macro Defect Free Polymer-Cement Composites, *Key Engineering Materials*, 466, 65-72, Jan, 2011.
- Ekincioglu, O., Ozkul, M. H., Struble, L. J., and Patachia, S., Optimization of Material Characteristics of Macro-Defect Free Cement, *Cement and Concrete Composites*, 34(4), 556-565, Apr, 2012a.

- Ekincioglu, O., Ozkul, M. H., Patachia, S., and Moise, G., Effect of TiO<sub>2</sub> Addition on the Properties of Macro Defect Free Cement, in *7th Asian Symposium on Polymers in Concrete, ASPIC2012*, 297-308, Ozkul, M. H., et al. (eds.), Istanbul, Turkey, 2012b.
- Hasegawa, M., Kobayashi, T., and Pushpalal, G. K. D., A New Class of High Strength, Water and Heat Resistant Polymer-Cement Composite Solidified by an Essentially Anhydrous Phenol Resin Precursor, *Cement and Concrete Research*, 25(6), 1191-1198, Aug, 1995.
- Lewis, J. A., and Boyer, M. A., Effects of an organotitanate cross-linking additive on the processing and properties of macro-defect-free cement, *Journal of Advanced Cement Based Materials*, 2(1), 2-7, Jan, 1995.
- Liutkus, J. J., and Kovac, C. A., Polysiloxane modified cement, *United States Patent*, No: 4780754, 1988.
- Lynn, M. E., and Durey C. A., Cementitious products, *United States Patent*, No: 5147459, 1992.
- Mojumdar, S. C., Processing-Moisture Resistance and Thermal Analysis of Macro-Defect-Free Materials, *Journal of Thermal Analysis and Calorimetry*, 64(3), 1133-1139, Jun, 2001.
- Ohama, Y., Improvement in water resistance of macro defect free cements using ordinary portland cement in *Proceedings of the 3rd Japan Congress on Materials Research*, The Society of Materials Science, 192-195, Kyoto, Japan, 1993.
- Ohama, Y., *Handbook of Polymer-Modified Concrete and Mortars-Properties and Process Technology*, Noyes Publications, New Jersey, 1995.
- Poon, C. S., and Groves G. W., The microstructure of macrodefect free cement with different polymer contents and the effect on water stability, *Journal of Materials Science*, 23(2), 657-660, Feb, 1988.
- Poon, C. S., The influence of Admixtures on the Microstructure and Water Stability of Macro-Defect Free Cement, *Journal of Materials Science Letters*, 17(18), 1593-1595, Sep, 1998.
- Popoola, O. O., Kriven, W. M., and Young, J. F., Microstructural and Microchemical Characterization of a Calcium Aluminate-Polymer Composite (MDF Cement), *Journal of American Ceramic Society*, 74(8), 1928-1933, Aug, 1991.
- Pushpalal, G. K. D., Kobayashi, T., and Hasegawa, M., High Alumina Cement-Phenol Resin Composite: Water Resistivity and Effect of Post Hydration of Unreacted Cement on Durability, *Cement and Concrete Research*, 27(9), 1393-1405, Sep, 1997.
- Pushpalal, G. K. D., Kobayashi, T., Kawano, T., and Maeda, N., The Processing, Properties, and Applications of Calcium Aluminate-Phenol Resin Composite, *Cement and Concrete Research*, 29(1), 121-132, Jan, 1999.
- Russell, P. P., *Processing Studies of Macro-Defect-Free Cement and Investigation of Chemical Modifiers to Improve the Water Resistance of the Composite*, M.S. Thesis, University of Illinois at Urbana-Champaign, IL, USA, 1991.
- Santos, R. S., Rodrigues, F. A., Segre, N., and Joeques, I., Macro-defect free cements influence of poly(vinyl alcohol), cement type, and silica fume, *Cem Concr Res*, 29(5), 747-751, May, 1999.
- Sinclair, W., and Groves G. W., The microstructure of high strength cement pastes in *Proceedings of the Materials Research Society Symposia*, Young, J.F. (ed.), 42, 31-37, Boston, Massachusetts, USA, 1984.
- Sinclair, W., and Groves, G. W., High Strength Cement Pastes - Part 1: Microstructures, *Journal of Materials Science*, 20(8), 2846-2852, Aug, 1985.
- Tan, L. S., *Processing-property interactions in macro-defect-free cement*, MSc Thesis, University of Illinois at Urbana-Champaign, IL, USA, 1992.
- Titchell, I., Environmental degradation of macrodefect free cements, Part I: Mechanical properties investigation, *Journal of Materials Science*, 26(5), 1199-1204, Jan, 1991.
- Walberer, J. A., and McHugh, A. J., Processing/Property/Structure Interactions in a Calcium Aluminate-Phenol Resin Composite, *Advanced Cement Based Materials*, 8(3-4), 91-100, Oct, 1998.