

INVESTIGATION EFFECT OF THE AGE ON THE COMPRESSIVE STRENGTH OF CONCRETE THROUGH USING ULTRASONIC PULSE VELOCITY

QADRI AHMED YOUSIF¹, IDRIS BEDIRHANOGLU², MEHMET ENVER AYDIN³, and
ZIWAR ZEBARI⁴

¹*Dept of Physics, Masaka Company, Duhok, Iraq*

²*Dept of Civil Engineering, New York University Abu Dhabi, Abu Dhabi, UAE,*

³*Dept of Physics, Dicle University, Diyarbakir, Turkey*

⁴*Dept of Physics, Ministry of Education, Duhok, Iraq*

In this study, effect of the age on the strength development of concrete was investigated. For this purpose, specimens casted with ready mix concrete for different grades of concrete obtained from ready-mix concrete firms available in Diyarbakir city which is the one of the biggest cities of Turkey. A few sets with different grade of concrete cube specimens were used in the experimental work. Each set includes more than 40 specimens. For measuring concrete strength development, two different tests were used which are ultrasonic pulse velocity testing (UPV) and uniaxial compressive strength testing. After a bunch of UPV and compressive strength tests, strength development for early ages were evaluated and defined. By this work it is targeted to define the path of strength development of certain grades of concrete used in the east regions of Turkey. Another aim of the work is to be able to determine concrete strength through non-destructive UPV tests. As a result of the work, it was seen that concrete strength development for early ages are not linearly proportional to the age. And furthermore, UPV measurements can give important information relating progress in concrete strength.

Keywords: Nondestructive test (NDT), Ready-mix concrete.

1 INTRODUCTION

Concrete is a composite material consisting of water, cement, sand and gravel. It is a most widely used material in building construction, because of easily availability of aggregate that forms around 70% of the volume of concrete.

Because of it, concrete quality that is used in any field of construction (i.e. buildings, bridges, roads) must be checked and controlled. Fortunately, today technology has more techniques and science branches that can be used in this area.

One of the techniques of physics and engineering sciences widely used to identify concrete quality, and physical or mechanical properties are called non-destructive testing (NDT), (ACI 228.2R). NDT is a technique used to inspect the physical and mechanical properties of a material without causing any damage. In NDT, the major purpose is to determine errors in a piece being tested. One of the most important factors in the development of a measurement and control system, called Non-Destructive Inspection, is the need to minimize or even eliminate the risk that

caused by destructive testing method which is the fundamental method of classical quality control. Quality control of the material with NDT is economical due to not damaging the materials. Non-destructive testing methods are used almost as a quality control tool at every step of production, during operation, during periodic maintenance and during the development of new products. Non-destructive testing evaluation is fast and sensitive (Hellier 2003).

The material inspection, which means the examination of the structural and internal properties of the materials, is divided into two sections; non-destructive testing and destructive testing (DT). Non-destructive material inspection can be used for different purposes such as examining of defects that occur in materials because of various reasons. Ultrasonic pulse velocity testing method (UPV) is one of the NDT test methods that works by sending high sound frequency wave through the material for analyzing physical and mechanical properties (Hellier 2003).

UPV method is used to ensure the properties of concrete and natural rocks. In this study, the physical and mechanical properties of concrete are aimed to define through measuring the velocity of ultrasonic pulse velocity. This test is carried out by travelling a pulse of ultrasonic wave energy through concrete and measuring the pass time of the pulse. Higher velocities indicate good quality and continuity of the material, but slower velocities through concrete structures indicate low-quality concrete or may indicate concrete with defects (cracks or voids) (Neville 1996 and Luthi 2013).

The UPV method is being used to evaluate the quality of concrete with measurement of velocity propagating through the bulk of the material to find out the quality of concrete whether is good or bad in terms of density, uniformity, homogeneity etc. (IS 1992).

Compressive strength of concrete is evaluated more commonly by destructive methods compared to nondestructive testing. Destructive testing is the most reliable method for measuring properties of the concrete. On the other hand, this method damages the material and costs more labor. So, it is vital to improve new techniques for measuring properties of concrete. At this aspect UPV is a good alternative however more researches are needed to improve the reliability of the technique. For that reason, significant number of experiments are needed to be done with different types of concrete in different regions. This point has been our main source of motivation for carrying this study.

In this study assessing the effect of the age of the concrete on the compressive strength of concrete was investigated.

2 EXPERIMENTAL WORK

2.1 Specimens and Tests

Three groups of cube samples were tested in this section. Each group consisted of at least 40 samples. A total of at least 130 samples were prepared. Weights of each sample were measured, UPV and axial compression tests were performed (Figure 1). Therefore, three data for each sample were generated. These measurements were made on the days that we specified earlier. During tests specimens were kept in water with around 21 °C.

All these samples were taken from three different locations. So, we can split these samples into three groups. The first group is the C20 concrete produced by the Emirler Concrete Plant for the text building. The second group is taken from Bes Concrete Plant and has 25 concrete classes. The third group is again from Bes Concrete Plant C30 concrete.



Figure 1. Testing set up of the UPV test.

After 24 hours from casting, specimens were removed from the plastic mold with air pressure. The first measurements were done on three specimens and others were held in water. In each day at least three specimens were tested. The UPV and compressive strength tests were made on 1, 2, 3, 4, 5, 6, 7, 8, 9, 10, 14, 21 and 28 days.

2.2 Experimental Results

Compressive strength test was conducted by using three specimens at each testing day. Generally, for each day of testing compressive and UPV tests were carried out on three specimens while in order to have an idea about other specimens UPV test were carried on all other specimens, too. At each time of testing minimum three specimens were used and mean values of these three specimens were used to draw graphs given in Figures 2-3. Figures 2-3 show relationship between age and compressive strength of concrete both with UPV measurement and compressive strength tests for three groups of specimens. All graphs clearly show that strength of concrete suddenly increases with age at very early first few days. After, the increase in compressive strength stops suddenly for next few days. After few days of recession, compressive strength of concrete starts to increase in very slow manner. Relationships between UPV and compressive tests were given in Figure 4. It can be easily concluded that there are some reasonable relations between UPV and compressive strength for different ages of different grades of concrete.





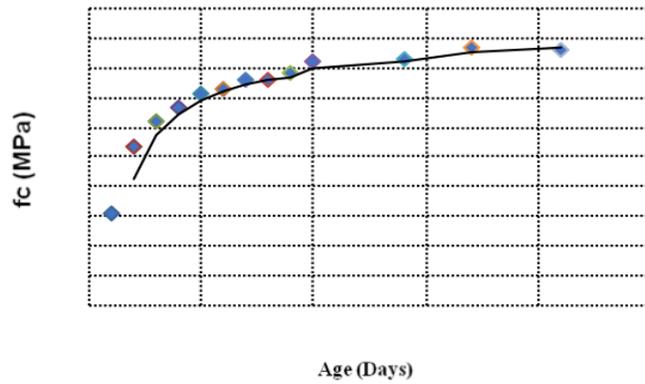



Figure 2. Compression strength and age relationships graphs for all three groups.

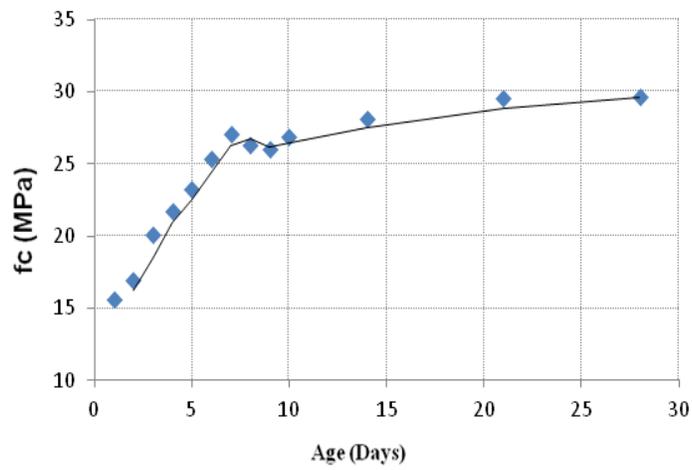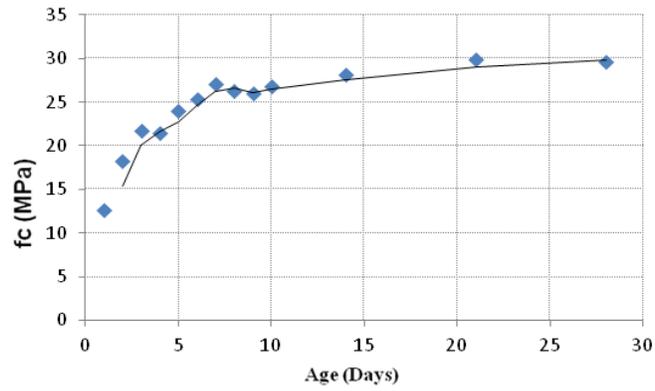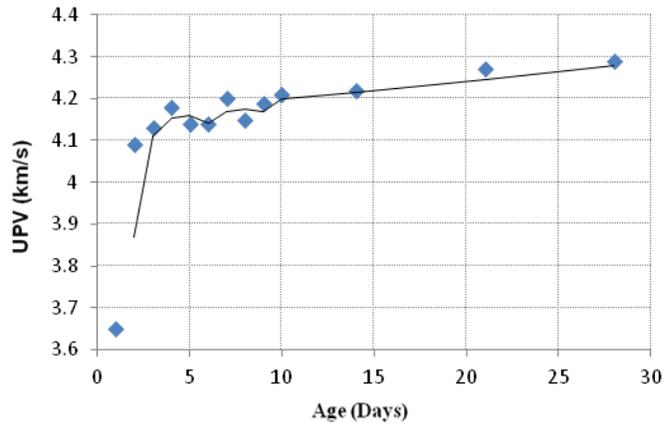

Group 1

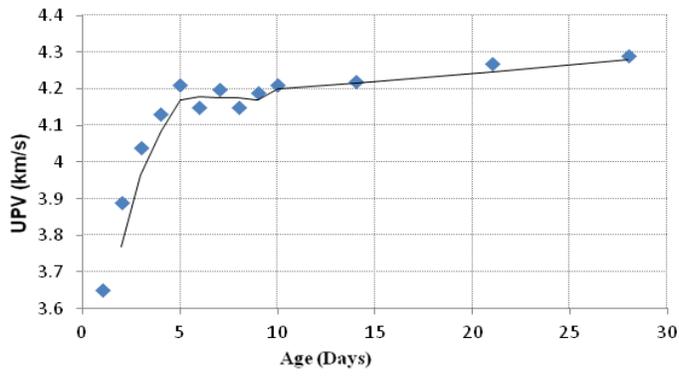

Group 2

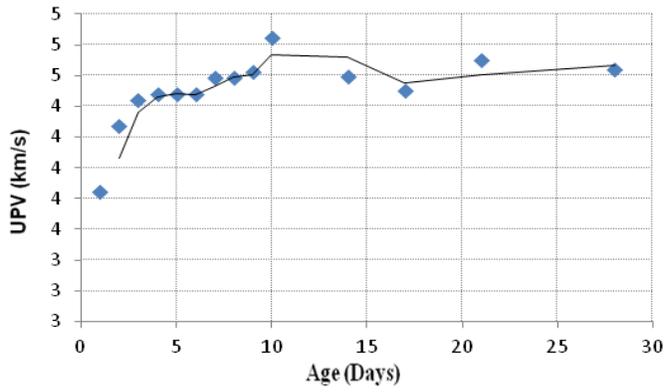

Group 3

Figure 3. UPV and age relationships graphs for all three groups.

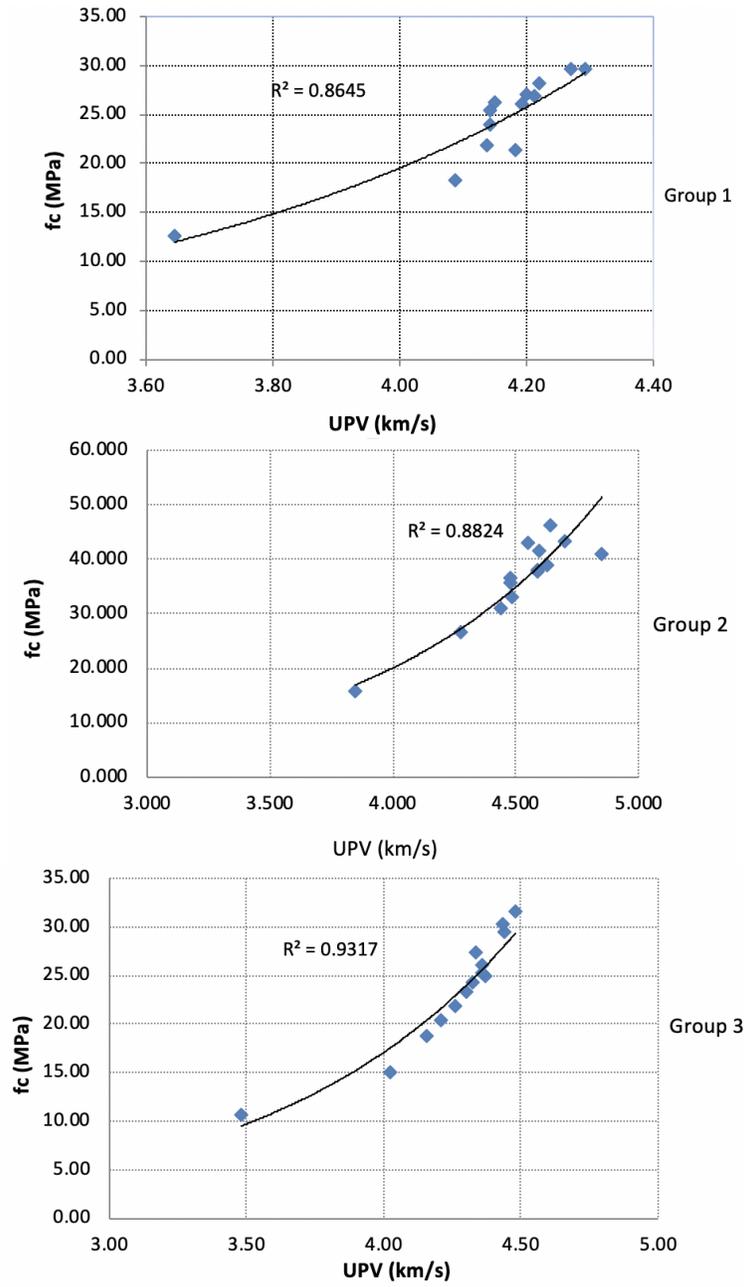


Figure 4. UPV and compressive strength relationships for all three groups.

3 SUMMARY

This paper investigated the effect of age of concrete on the strength development through using UPV measurement compared with compression tests. This relation is schematically illustrated as in Figure 5. As a summary it can be concluded that UPV values increase with age of concrete both in case of UPV and compression tests. However, this increase is not linear. Another important finding is recession in UPV values at certain ages such as between 5-10 days where this was not seen in relation between compressive strength and age of concrete.

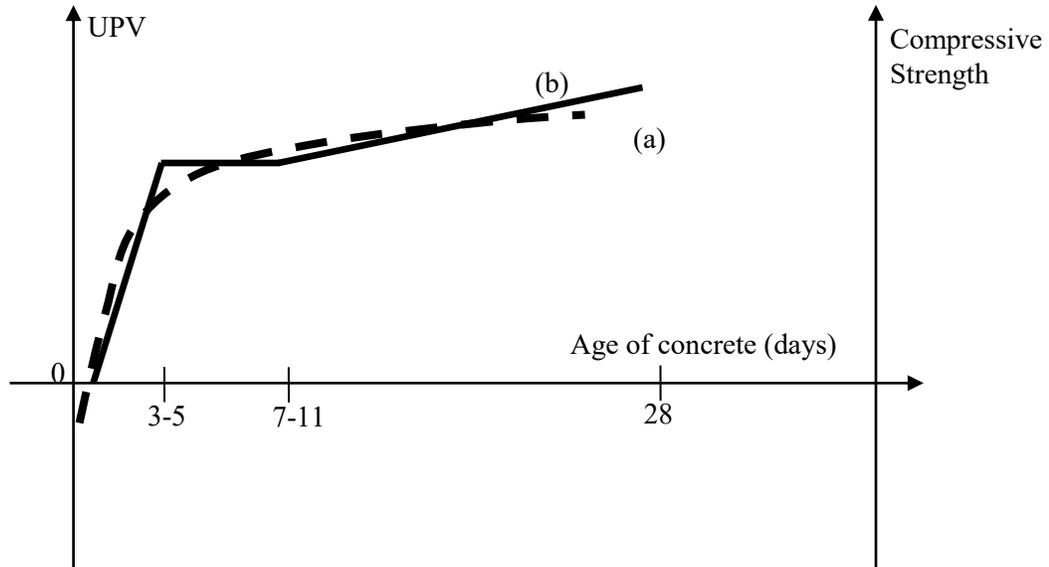


Figure 5. Schematic representation of relationships between a) UPV and age of concrete, b) compressive strength and age of concrete.

Acknowledgments

We would like to thank our friends Vaheel Abdullah, Melik Osal and Emre Güven for their help during experiments. We would like to thank the Laboratory of Civil Engineering Department of Dicle University and Dicle University Department of Physics for their facilities that they provide. We appreciate the financial support provided by MASAKA General Trading – Import and Export LTD Company, KRG, Iraq.

References

- Abdullah, V., Aydın M. and Bedirhanoglu, I., Beton Elastisite Modülünün Ultrasonik Ses Dalgası Yayılma Hızı İle Tahmin (Prediction of Elastic Modulus of Concrete Through Using Ultrasonic Pulse Velocity), *Dicle Üniversitesi Mühendislik Fakültesi Mühendislik Dergisi*, 8(3), 475-484, 2017.
- ACI 228.2R, *Non-destructive Test Methods for Evaluation of Concrete in Structures*.
- Bedirhanoglu, I., A Practical Neuro-Fuzzy Model for Estimating Modulus of Elasticity of Concrete, *Structural Engineering and Mechanics*, 51(2), 249-265, 2014.
- Hellier, C., *Handbook of Non-Destructive Testing Evaluation*, McGraw. Hill, Chapter 1, 2003.
- Luthi, T., *Non-Destructive Evaluation Method, 2003-2013*, Anax Imperator, Micro X-ray Tomographic View, Iwan Jerjen, Empa, 2013.
- Neville, A. M., *Properties of Concrete*, 4th edition. John Wiley and Sons, Inc., New York. IS, 1996.

- Zebari, Z., Bedirhanoglu, I., and Aydin M., Beton Basınç Dayanımının Ultrasonic Ses Dalgası Yayılma Hızı İle Tahmin (Prediction of Compressive Strength of Concrete Through Using Ultrasonic Pulse Velocity), *Dicle Üniversitesi Mühendislik Fakültesi Mühendislik Dergisi*, 8(1), 43-52, 2017.
- Yousif, Q. A., *Beton Yaşının Basınç Dayanımı Üzerine Olan Etkisinin Ultrases Yöntemi İle Belirlenmesi (In Turkish) (Determining Effect of the Age of the Concrete on the Compressive Strength Through with UPV)*, MSc Thesis, Institute of Science, Dicle University, Diyarbakir, 2018.